

**Date of Issue:** July 20, 1998  
**Effective Date:** August 19, 1998

**SUPPLEMENT 1 to API Specification 15HR,  
Specification for High Pressure Fiberglass Line Pipe  
Second Edition, April 1, 1995**

**Preface**

This Supplement includes a revision approved by special letter ballot of the API Subcommittee on Fiberglass and Plastic Tubulars in 1998. This revision shall be effective on the effective date shown above.

**Page 6, Par. 5.4.2.** Delete this paragraph.



**American  
Petroleum  
Institute**

1220 I Street, Northwest  
Washington, D.C. 20005-4070  
202-682-8000

# **Specification for High Pressure Fiberglass Line Pipe**

**API SPECIFICATION 15HR  
SECOND EDITION, APRIL 1, 1995**

**American Petroleum Institute**  
1220 L Street, Northwest  
Washington, D.C. 20005



# **Specification for High Pressure Fiberglass Line Pipe**

**Exploration and Production Department**

API SPECIFICATION 15HR  
SECOND EDITION, APRIL 1, 1995

**American  
Petroleum  
Institute**



## SPECIAL NOTES

API publications necessarily address problems of a general nature. With respect to particular circumstances, local, state, and federal laws and regulations should be reviewed.

API is not undertaking to meet the duties of employers, manufacturers, or suppliers to warn and properly train and equip their employees, and others exposed, concerning health and safety risks and precautions, nor undertaking their obligations under local, state, or federal laws.

Information concerning safety and health risks and proper precautions with respect to particular materials and conditions should be obtained from the employer, the manufacturer or supplier of that material, or the material safety data sheet.

Nothing contained in any API publication is to be construed as granting any right, by implication or otherwise, for the manufacture, sale, or use of any method, apparatus, or product covered by letters patent. Neither should anything contained in the publication be construed as insuring anyone against liability for infringement of letters patent.

Generally, API standards are reviewed and revised, reaffirmed, or withdrawn at least every five years. Sometimes a one-time extension of up to two years will be added to this review cycle. This publication will no longer be in effect five years after its publication date as an operative API standard or, where an extension has been granted, upon republication. Status of the publication can be ascertained from the API Authoring Department [telephone (214) 953-1101]. A catalog of API publications and materials is published annually and updated quarterly by API, 1220 L Street, N.W., Washington, D.C. 20005.

This document was produced under API standardization procedures that ensure appropriate notification and participation in the developmental process and is designated as an API *standard*. Questions concerning the interpretation of the content of this standard or comments and questions concerning the procedures under which this standard was developed should be directed in writing to the director of the Exploration and Production Department, American Petroleum Institute, 700 North Pearl, Suite 1840, Dallas, Texas 75201. Requests for permission to reproduce or translate all or any part of the material published herein should also be addressed to the director.

API publications may be used by anyone desiring to do so. Every effort has been made by the Institute to assure the accuracy and reliability of the data contained in them; however, the Institute makes no representation, warranty, or guarantee in connection with this publication and hereby expressly disclaims any liability or responsibility for loss or damage resulting from its use or for the violation of any federal, state, or municipal regulation with which this publication may conflict.

API standards are published to facilitate the broad availability of proven, sound engineering and operating practices. These standards are not intended to obviate the need for applying sound engineering judgment regarding when and where these standards should be utilized. The formulation and publication of API standards is not intended in any way to inhibit anyone from using any other practices.

Any manufacturer marking equipment or materials in conformance with the marking requirements of an API standard is solely responsible for complying with all the applicable requirements of that standard. API does not represent, warrant, or guarantee that such products do in fact conform to the applicable API standard.

Copyright © 1995 American Petroleum Institute

## CONTENTS

	Page
1 SCOPE .....	1
1.1 Purpose.....	1
1.2 Applications .....	1
1.3 Unit Conversion .....	1
1.4 Availability of Test Results .....	1
2 REFERENCES .....	2
2.1 General.....	2
2.2 Requirements .....	2
2.3 Equivalent Standards.....	2
3 GLOSSARY (DEFINITIONS, ABBREVIATIONS).....	2
3.1 Definitions.....	2
3.2 Abbreviations .....	2
4 PURCHASING GUIDELINES .....	3
4.1 General.....	3
4.2 Pressure Ratings.....	3
4.3 Components .....	3
5 DESIGN .....	3
5.1 Performance Requirements.....	3
5.2 Dimensions .....	4
5.3 Threaded End Connections .....	5
5.4 Requalification .....	6
6 PROCESS OF MANUFACTURE AND MATERIAL .....	6
6.1 Process of Manufacture.....	6
6.2 Materials .....	6
7 QUALITY PROGRAM.....	6
7.1 Quality Manual .....	6
7.2 Process Control Requirements.....	6
7.3 Quality Control Equipment.....	6
7.4 Quality Control Tests .....	7
7.5 Inspection and Rejection.....	7
7.6 Quality Control Records Requirements .....	7
8 PUBLISHED VALUES .....	8
8.1 Published Properties.....	8
8.2 Published Dimensions.....	8
9 EQUIPMENT MARKING .....	9
9.1 Methods.....	9
9.2 Components Shall Be Marked with the Following .....	9
10 HANDLING, PACKAGING, STORING, AND SHIPPING REQUIREMENTS ..	9
10.1 Coupling Makeup and Thread Compounds .....	9
10.2 Thread Protectors .....	9
10.3 Flange Face Protectors .....	9
10.4 Packaging, Shipping and Handling Requirements.....	9
APPENDIX A—PRODUCT CHARACTERISTICS .....	11
APPENDIX B—METRIC CONVERSIONS.....	13

APPENDIX C—TEST METHOD FOR DETERMINATION OF DEGREE OF CURE BY DIFFERENTIAL SCANNING CALORIMETRY (DSC) .....	15
APPENDIX D—DETERMINATION OF THE HOOP TENSILE MODULUS AND POISSON'S RATIO .....	17
APPENDIX E—PURCHASER INSPECTION .....	19
APPENDIX F—DETERMINATION OF THE AXIAL TENSILE POISSON'S RATIO .....	21
APPENDIX G—SERVICE (DESIGN) FACTORS .....	23
APPENDIX H—DATA SHEET .....	25
APPENDIX I—USE OF API MONOGRAM .....	27
PUBLICATIONS LIST .....	29
Figures	
1—Typical Test Setup to Determine Hoop Tensile Modulus and Poisson Ratio.....	17
Tables	
1—Tolerance on Dimensions .....	4
2—Thread Sizes .....	5
3—Visual Standards .....	8

## FOREWORD

This specification is under the jurisdiction of the API Committee on Standardization of Plastic Pipe and includes changes to the previous edition approved by letter ballot through February 1994. Bar notations in the margins have been used to identify changes from the previous edition.

*This standard shall become effective on the date printed on the cover but may be used voluntarily from the date of distribution.*

# Specification for High Pressure Fiberglass Line Pipe

## 1 Scope

### 1.1 PURPOSE

**1.1.1** This specification was formulated to provide for the availability of safe, dimensionally and functionally interchangeable high pressure fiberglass line pipe with a Specification 15HR Standard Pressure Rating from 500 psi to 5000 psi, inclusive, in 250 psi increments. This specification is limited to mechanical connections.

**1.1.2** Technical content provides requirements for performance, design, materials, tests and inspection, marking, handling, storing and shipping.

**1.1.3** Critical components are items of equipment having requirements specified in this document.

### 1.2 APPLICATIONS

#### 1.2.1 Equipment

This specification covers fiberglass pipe utilized for the production of oil and gas. Specific equipment covered by this specification is listed as follows:

- High pressure line pipe and couplings.
- Fittings.
- Flanges.
- Reducers and adapters.

#### 1.2.2 Service Conditions

The standard service conditions for Specification 15HR Standard Pressure Rating are as follows:

- Service life is 20 years.
- Service temperature is 150°F.
- The fluid environment is salt water.

Axial loads shall include end loads due to pressure and bending, where the radius of curvature of the pipe divided by the outside radius of the pipe shall be greater than or equal to 1200.

Cyclic pressure variation shall include 3,000 cycles from 0 to 120% of Specification 15HR Standard Pressure Rating. Cyclic pressure variation shall include  $10^9$  cycles with an R value of 0.9.

(R = minimum pressure divided by maximum pressure).

Service conditions other than the standard Specification 15HR conditions are discussed in Par. 5.1.1 and Appendix G.

### 1.3 UNIT CONVERSION

A decimal/inch system is the standard for the dimensions shown in this specification. Nominal sizes will continue to

be shown as fractions. For the purposes of this specification, the fractions and their decimal equivalents are equal and interchangeable. Metric conversions are described in Appendix B.

### 1.4 AVAILABILITY OF TEST RESULTS

The Manufacturer shall prepare a report as outlined below:

	Outline of Report Requirements.
Par. 5.1	Manufacturers Make-Up Procedure.
Par. 5.1.1	Report per ASTM D2992 and Par. 5.1.1.
Par. 5.1.2	Report per ASTM D1599 and Par. 5.1.2.
Par. 5.1.3	Report per ASTM D2143 and Par. 5.1.3.
Par. 5.1.4	Report per ASTM D1598 and Par. 5.1.4.
Par. 5.4.1	Report per ASTM D2992 and calculation of requalification LTHS.
Par. 8.1.c	Report per manufacturers written test procedure.
Par. 8.1.d	Report per Appendix D.
Par. 8.1.e	Report per Appendix D.
Par. 8.1.f	Report per Appendix F.
Par. 8.1.g	Report per ASTM D2105.
Par. 8.1.h	Report per ASTM D1599.
Par. 8.2	For each qualified pipe, include a table showing inside diameter, minimum reinforced wall thickness, and hoop stress at rated pressure.
Appendix A	For all qualified components product characteristics outlined in Appendix A.
Manufacturer's Table	A table listing all qualified components by size and pressure rating.

This report shall be kept on file with the Manufacturer and a copy shall be available on request to each purchaser. Any variance from the above test procedures voids the test as having been conducted according to API Specification 15HR. Any user company may witness representative testing of pipe and connections, observe Manufacturer's testing procedures, or inspect test apparatus.

Prior to presenting results of tests in verbal or written reports, articles, or advertisements and stating that the tests were made in accordance with API Specification 15HR the Manufacturer shall complete the report described above. This copy must be dated and reported test results certified by a management official of the company. It shall be the responsibility of the manufacturing company to maintain copies of the certified tests results for a minimum of five years from the date the manufacturing of the product is discontinued.

When the results of the tests are presented in verbal or written reports, articles, or advertisements and state that the



tests were made in accordance with API Specification 15HR; such reports, articles, or advertisements must be worded in a fashion which will not imply that the American Petroleum Institute either recommends or disapproves use of the subject components.

## 2 References

### 2.1 GENERAL

This specification includes by reference, either in total or in part, the most current issue of the following standards, unless a specific edition is listed.

#### API

- Bul 5A2 *Bulletin on Thread Compounds for Casing, Tubing and Line Pipe.*
- STD 5B *Specification for Threading, Gaging, and Thread Inspection of Casing, Tubing and Line Pipe Threads.*
- RP 5B1 *Recommended Practice for Gaging and Inspection of Casing, Tubing and Line Pipe Threads.*
- Spec 15LR *Specification for Low Pressure Fiberglass Linepipe.*
- RP 15TL4 *Recommended Practice for Care and Use of Fiberglass Tubulars.*

#### ANSI

- B16.5 *Pipe Flanges and Flanged Fittings.*

#### ASTM

- D1598 *Test Method for Time-to-Failure of Plastic Pipe Under Constant Internal Pressure.*
- D1599 *Test Method for Short-Time, Hydraulic Failure Pressure of Plastic Pipe, Tubing and Fittings.*
- D2105-85 *Test Method for Longitudinal Tensile Properties of Reinforced Thermosetting Resin Pipe and Tube. (1985 edition)*
- D2143 *Test Method for Cyclic Pressure Strength of Reinforced, Thermosetting Plastic Pipe.*
- D2584 *Test Method for Ignition Loss of Cured Reinforced Resins.*
- D2992 *Method for Obtaining Hydrostatic Design Basis for Reinforced Thermosetting Resin Pipe and Fittings.*
- D3567 *Method for Determining Dimensions of Reinforced Thermosetting Resin Pipe (RTRP) and Fittings.*

### 2.2 REQUIREMENTS

Requirements of other standards included by reference in this specification are essential to the safety and interchangeability of the equipment produced.

### 2.3 EQUIVALENT STANDARDS

Other nationally or internationally recognized standards

shall be submitted to and approved by API for inclusion in this specification prior to use as equivalent standards.

## 3 Glossary (Definitions, Abbreviations)

### 3.1 DEFINITIONS

**3.1.1 acceptance criteria:** Defined limits placed on characteristics of materials, products, or services.

**3.1.2 adapters:** Appurtenances that allow connecting components with different joining systems.

**3.1.3 component:** Any high pressure line pipe, pipe connection, fitting, flange, adapter, reducer, or end of outlet connections covered by this specification.

**3.1.4 date of manufacture:** Date of cure.

**3.1.5 fiberglass:** A generic term for glass fiber reinforced thermosetting resins.

**3.1.6 fittings:** Tees, 90's and 45's.

**3.1.7 flanges:** Face flanges with bolt circle and face dimensions per ANSI B16.5.

**3.1.8 may:** Used to indicate that a provision is optional within this specification.

**3.1.9 pi tape:** A tape used to measure circumference.

**3.1.10 prime connection:** The Manufacturer's standard joining system for straight pipe.

**3.1.11 records:** Retrievable information.

**3.1.12 reducers:** Components that allow pipes of different sizes to be connected.

**3.1.13 serialization:** Assignment of a unique code to each individual component to maintain traceability.

**3.1.14 shall:** Used to indicate that a provision is mandatory within this specification.

**3.1.14 should:** Used to indicate that a provision is not mandatory but recommended as good industry practice within this specification.

**3.1.15 Specification 15HR Standard Pressure Rating:** The Manufacturer's pressure rating determined in accordance with API Specification 15HR.

**3.1.16 visual examination:** Examination of parts and equipment for visible defects in material and workmanship.

### 3.2 ABBREVIATIONS

ANSI	American National Standards Institute
API	American Petroleum Institute
ASTM	American Society for Testing and Materials
DSC	Differential Scanning Calorimetry
LCL	95% Lower Confidence Limit.
LTHS	Long-Term Hydrostatic Strength

## 4 Purchasing Guidelines

### 4.1 GENERAL

This section provides recommended guidelines for inquiry and purchase of Specification 15HR pipe or component. These guidelines consist of data sheets to be completed by the Purchaser.

#### 4.1.1 Data Sheet

The data sheet is designed to perform two functions:

- Assist the Purchaser in the procurement of the proper pipe or component.
- Assist the Purchaser in communicating his particular needs and requirements, as well as information on the environment, to the Manufacturer for his use in designing and producing pipe or component.

#### 4.1.2 Use

A copy of the data sheet should be completed as accurately as possible.

A copy of the data sheet should then be attached to the purchase order or request for proposal.

Appendix H provides a format to document service conditions and requirements for ordering high pressure fiberglass components.

### 4.2 PRESSURE RATINGS

It is recommended that the pipe be purchased by pressure rating. The API Standard Pressure Ratings are from 500 psig through 5,000 psig in 250 psig increments. The user should purchase pipe suitable for the specific service conditions.

### 4.3 COMPONENTS

Components, other than pipe, should be ordered on the basis of thread size and pressure rating.

## 5 Design

### 5.1 PERFORMANCE REQUIREMENTS

#### 5.1.1 Pipe and Prime Connection

The published Specification 15HR Standard Pressure Rating shall be determined by the following method:

ASTM Standard Method D 2992 Procedure B with free ends shall be performed at 150° F or higher. Each specimen that fails beyond 6,000 hours shall have a prime connection at the center of each specimen. The number of samples and distribution of failure points shall be as follows:

10 — 1,000 hours	at least 4
1,000 — 6,000 hours	at least 3
Beyond 6,000 hours	at least 6
Total Hours	at least 18

The test sample shall be a size no smaller than 2 inch nominal diameter, with an outside diameter to reinforced wall thickness ratio of 10 or less for scaling to be unlimited. If an outside diameter to reinforced wall thickness ratio of greater than 10 is used, then the tested ratio shall be the lower limit for scaling. The samples shall be assembled by the Manufacturer's documented make-up procedure. Any ASTM D 2992 test started after September 15, 1988 shall have DSC (Differential Scanning Calorimetry) data on each sample in accordance with Appendix C.

The published Specification 15HR Standard Pressure Rating shall be calculated by the following equation and rounded down to the nearest integer multiple of 250 psi:

$$P_r = S_s \times S_f \times \frac{R_o^2 - R_i^2}{R_o^2 + R_i^2} \quad \text{Equation 1}$$

Where:

$P_r$  = Specification 15HR Standard Pressure Rating, psi.

$S_s$  = 95% Lower Confidence Limit (LCL) of the Long-Term Hydrostatic Strength (LTHS) @ 20 years per ASTM D 2992 Procedure B @ 150°F or higher psi.

$S_f$  = 0.67 service (design) factor (See Appendix G.)

$R_o$  = radius of the pipe at the outside of the minimum reinforced wall thickness inches.

$R_i$  = radius of the pipe at the inside of the minimum reinforced wall thickness inches.

Scaling based on the LCL shall be done using Equation 1.

If only one regression test as defined above is conducted, the Specification 15HR Standard Pressure Rating shall be based on that test and shall be valid up to and including the test temperature. Additional regression tests as defined above may be conducted. If additional regression tests as defined above are conducted the following rules apply.

- Pressure ratings at temperatures between the test temperatures shall be based on a linear interpolation between closest two temperatures at which tests have been conducted. No extrapolation beyond the temperatures at which data is available is allowed. The pressure rating below the lowest temperature at which data is available shall be based on the lowest temperature at which data is available.

- The Specification 15HR Standard Pressure Rating shall be at 150° F. This rating shall be based on data at 150° F if available, otherwise, this rating shall be interpolated from data above and below 150° F.

- The proof test pressure shall be based on the Specification 15HR Standard Pressure Rating.

#### 5.1.2 Short-Term Failure Pressure

The burst pressure capability of components shall be

demonstrated by pressure testing two samples of each size, type and pressure rating of component in accordance with ASTM D 1599 (free end). Both samples shall be assembled using the Manufacturer's documented make-up procedures. Thread dimensions including taper, lead, angle, height, length, chamfer and stand-off, and reinforced wall thickness shall be recorded. Tests shall be conducted at ambient temperature. The ratio ( $R_4$ ) for 4 inch components is defined as follows:

$$R_4 = \frac{P_{b4}}{P_{r4}}$$

Where:

$R_4$  = Ratio of average failure pressure and Specification 15HR Standard Pressure Rating for 4 inch component.

$P_{b4}$  = Failure pressure (ASTM D 1599, free end) of 4 inch component qualified in accordance with Paragraph 5.1.4.

$P_{r4}$  = Specification 15HR Standard Pressure Rating for the 4 inch component qualified in accordance with Paragraph 5.1.4.

The Specification 15HR Standard Pressure Rating for other sizes of components shall meet the following criteria:

$$P_r \leq \frac{P_b}{R_4}$$

$P_r$  = Specification 15HR Standard Pressure Rating for component.

$P_b$  = Failure pressure of component (ASTM D 1599, free end).

### 5.1.3 Cyclic Pressure

The cyclic pressure capability of components shall be demonstrated by pressure testing two samples of each size, type and pressure class of component. Both samples shall be assembled by the Manufacturer's documented make-up procedure, including thread taper, lead, angle, height, length, chamfer and standoff. The number of pressure cycles applied and reinforced wall thickness shall be recorded. No failures shall occur at fewer than 5,000 pressure cycles from not more than 100 psig to at least 150% of the Specification 15HR Standard Pressure Rating. Tests shall be conducted at ambient temperature in accordance with ASTM D 2143 at up to 25 cycles per minute. The pipes threaded into the components shall be free-ended with at least 12 inches of pipe between the end closure and the components.

### 5.1.4 Static Pressure

The static pressure capability of components shall be demonstrated by pressure testing one sample of the largest

size manufactured in accordance with Specification 15HR up to size 4 inch, of each type and pressure class of component. Samples shall be assembled by the Manufacturer's documented make-up procedure. Thread dimensions including taper, lead, angle, height, length, chamfer and standoff; total test time and reinforced wall thickness shall be recorded. No failure shall occur within 6,000 hours at a minimum of 1.5 times the Specification 15HR Standard Pressure Rating. The end caps shall not be restrained. This test shall be conducted at 150° F or higher. The pipes threaded into the components shall be free-ended with at least 12 inches of pipe between the end closure and the fitting. Degree of cure shall be determined on each component by DSC test conducted in accordance with Appendix C prior to pressure testing. The temperature and pressure tolerances shall be in accordance with ASTM D 1598.

## 5.2 DIMENSIONS

### 5.2.1 Length

Full length joints of pipe shall be in lengths according to the following schedule measured to the nearest 1.0 foot.

Length 1	Length 2	Length 3
15 to 21 feet	21 to 34 feet	34 or more feet

Jointers (two pieces coupled to make a standard length) shall constitute no more than 5 percent of the full length joints of the order; but no length used in making a jointer shall be less than 5 feet.

### 5.2.2 Dimensional Tolerances

Tolerances on inside diameter, total wall thickness, minimum reinforced wall thickness, and outside diameter are defined in Table 1.

Table 1—Tolerance on Dimensions

	Tolerance
Total Wall Thickness	+22.5% -0%
Reinforced Wall Thickness	+22.5% -0%
Outside Diameter, D, is governed by the inside diameter and wall thickness.	
Nominal Sizes (Inches)	Minimum Inside Diameter (Inches)
1	0.90
1 1/2	1.350
2	1.870
2 1/2	2.345
3	2.720
3 1/2	3.300
4	3.690
5	4.300
6	5.300
8	7.625

### 5.2.3 FLANGES

Flange bolt circle and face dimensions shall be in accordance with ANSI B16.5.

### 5.3 THREADED END CONNECTIONS

#### 5.3.1 General

Pipe shall be furnished as specified in the purchase order, with any of the following end finishes.

- Threaded and Coupled.
- Threaded Ends Without Couplings.
- Integral Joints.
- Alternate Pipe Thread.

#### 5.3.2 Standard Thread Design

- Pipe threads shall conform to API Standard 5B: *Threading, Gaging and Thread Inspection of Casing, Tubing and Line Pipe*.

Threads, with the thread dimensions in Table 2.6a, External Upset Tubing Long Thread Dimension for Reinforced Thermosetting Resin Tubing and Table 2.3, Casing Long-Thread Dimensions.

For the purpose of this specification, lengths  $L_2$  and  $L_4$ , in API Standard 5B, Table 2.6a and Table 2.3 shall be minimum dimensions. Any extra threads shall be added to the tube side of the thread.

- Thread tolerances will be defined in API Standard 5B, Table 2.10, Tolerances in Linepipe Thread and Casing and Tubing Round Thread Dimensions.
- Each product with standard thread design shall be threaded with the thread size shown in Table 2.
- Round threads shall have a fully rounded thread root and crest as conceptually illustrated in API Standard 5B, Figure

2.4, Casing and Tubing Round Thread Form. For eight round threads, thread root radius shall be 0.017 in.  $\pm$  0.0015 in. Thread crest radius shall be 0.020 in.  $\pm$  0.0015 in.. For ten round threads, thread root radius shall be 0.014 in.  $\pm$  0.0015 in. Thread crest radius shall be 0.017 in.  $\pm$  0.0015 in.

#### 5.3.3 Alternate Pipe Connections

Alternate connections shall be allowed and shall be identified by the letters A.C. following the "15HR" or API monogram marking. Alternate pipe connections shall meet the performance requirements of this specification.

#### 5.3.4

- Gaging Practice for Standard Threads

The Manufacturer shall own or have access to master gages for each size of thread produced on products conforming to this specification. The Manufacturer shall also own or have access to working gages conforming to gaging practices and gage specifications in API Standard 5B for use in gaging the product threads, and shall maintain all working gages in such condition as to ensure that product threads gaged as required in API Standard 5B are acceptable under that specification except as noted in Paragraph 5.3.2 of this specification. Thread gaging procedures shall be in accordance with API Recommended Practice 5B1.

- Gaging Practice for Alternate Pipe Connections

The Manufacturer shall own or have access to gages and working gages.

- The use of master gages in checking product threads should be minimized. Such use should be confined to cases of dispute which cannot be settled by rechecking the working gage against the reference master. Good care should be exercised when the master gage is assembled on a product thread.

Table 2—Thread Sizes

Nominal Diameter	Thread Size	Maximum Pressure Rating (psi)	Nominal Diameter	Thread Size	Minimum Pressure Rating (psi)
1	1.660*	5,000	—	—	—
1 1/2	1.900*	3,750	1 1/2	2 3/8*	4,000
2	2 3/8*	2,750	2	2 7/8*	3,000
2 1/2	2 7/8*	2,500	2 1/2	3 1/2*	2,750
3	3 1/2*	2,750	3	4 1/2*	3,000
3 1/2	4*	2,250	3 1/2	4 1/2*	2,500
4	4 1/2*	2,250	4	5 1/2**	2,500
5	5 1/2**	2,250	—	—	—
6	7 5/8**	3,250	—	—	—
8	9 5/8**	2,000	—	—	—

\*API Standard 5B, Table 2.6a (External Upset Tubing Long Thread Dimensions for Reinforced Thermosetting Resin Tubing)

\*\*API Standard 5B Table 2.3 (Casing Long-Thread Dimensions)

#### Notes

- These pressures were selected using  $D_4$  from API Standard 5B as a maximum outside diameter, the API minimum inside diameter, and equation 1.  $S_s = 14,000$  psi.
- Components should be ordered on the basis of thread size and pressure rating.

## 5.4 REQUALIFICATION

### 5.4.1 Requalification Tests for Pipe and Prime Connection

Changes as described in Appendix A for previously qualified systems shall require the following minimum tests:

The long-term static LTHS shall be verified at 150° F, or higher temperature if so rated, after any changes as described in Appendix A by conducting the abridged ASTM D 2992 Procedure B (free-end) test as described below. Test samples shall be assembled by the Manufacturer's documented make-up procedure.

Minimum Number of Samples	Hours to Failure
2	10 to 100
2	100 to 1,000
2	Beyond 1,000

Test samples shall be a size no smaller than 2 in. nominal diameter. The same outside diameter to reinforced wall ratio (D/t) constraints as in Paragraph 5.1.1 shall apply for requalification.

The failure points from these tests shall be combined with the failure points determined during the initial testing. The regression line determined on the combined data shall be extrapolated to obtain a requalification LTHS. If the LTHS for the combined data is greater than or equal to the corresponding lower confidence limit (LCL), per ASTM D 2992 Annex A2, of the initial tests, then the initial LTHS and LCL may be used. Otherwise, the changed product shall be retested per Paragraph 5.1 to obtain a new LTHS and LCL.

### 5.4.2 Improved Product Qualification

If the LTHS calculated using only the six requalification points is higher than the original LTHS, the Manufacturer may increase the LTHS and LCL proportionally to a maximum of 150% of original LTHS and LCL. An increase in the LTHS and LCL beyond 150% requires complete retesting of the new product.

### 5.4.3 Requalification Tests for Other Components

The requalification tests of Paragraph 5.1.2, 5.1.3 and 5.1.4 shall be repeated after any change as described in Appendix A.

## 6 Process of Manufacture and Material

### 6.1 PROCESS OF MANUFACTURE

Pipe furnished to this specification shall be produced by filament winding (FW) or centrifugal casting (CC) methods.

Components furnished to this specification shall be produced by compression molding (CM), centrifugal casting

(CC), filament winding (FW) or resin transfer molding (RTM) methods.

## 6.2 MATERIALS

The reinforced wall of pipe and components shall consist of thermosetting polymers reinforced with glass fibers. Acceptable polymers may include epoxy resins, polyester resins and vinyl ester resins.

Note: Other resins and reinforcements shall be considered for inclusion in this standard when evidence is presented to show that they are suitable for the applications covered by this standard.

## 7 Quality Program

### 7.1 QUALITY MANUAL

The Manufacturer shall maintain a Quality Manual. All prior revisions shall be retained for a period of not less than five years.

### 7.2 PROCESS CONTROL REQUIREMENTS

Manufacturer shall institute and maintain a process documentation program to assure communication of approved manufacturing procedures to qualified receiving, manufacturing and quality control personnel and their respective supervisory personnel to include the following functions:

- Raw Material Acceptance.
- Allowable Mixing Procedure(s).
- Fabrication Practice(s).
- Cure Procedure(s).

It shall be the responsibility of the manufacturing company to maintain copies of the document for a minimum of five years from the date the manufacturing of the product is discontinued.

### 7.3 QUALITY CONTROL EQUIPMENT

#### 7.3.1 General

Equipment used to inspect, test or examine material or other equipment shall be identified, controlled, calibrated and adjusted at specified intervals in accordance with documented Manufacturer instructions, and consistent with referenced industry standards to maintain the accuracy required by this specification.

#### 7.3.2 Dimensional Measuring Equipment

Dimensional measuring equipment shall be controlled and calibrated by the Manufacturer's written specification.

#### 7.3.3 Pressure Measuring Devices

- Test pressure measuring devices shall be either pressure gages or pressure transducers and shall be accurate to  $\pm 0.5\%$  of full scale range or better.

- b. A dead weight testing device shall be available at the Manufacturer's facility to calibrate gages.
- c. All pressure measuring devices shall be calibrated once every six months to maintain the required accuracy or calibrated when subjected to unusual or severe conditions, such as, would render its accuracy questionable.

## 7.4 QUALITY CONTROL TESTS

### 7.4.1 Hydrostatic Mill Test

Each component and length of pipe including jointers, after being fully cured shall be hydrostatically tested at the Manufacturer's facility to 1.5 times the Standard Pressure Rating. Hydrostatic test pressure shall be maintained for a minimum of two minutes. For every fiftieth joint, test pressure shall be maintained for a minimum of ten minutes. No visual leaks or weeps are permitted in the pipes, components, or end connections. Tests shall include an attached coupling or integral joint and shall not have restrained ends. Test temperature shall be ambient.

### 7.4.2 Degree of Cure

Degree of cure shall be determined by differential scanning calorimetry (DSC) according to Appendix C at a minimum frequency of once per shift for each resin system used at each Manufacturer's facility. DSC tests, in accordance with Appendix C, shall also be conducted on fittings at a frequency of one per 100 units irrespective of size, type or pressure rating. The T<sub>g</sub> shall not be more than 5° C below the minimum values measured in 5.1.1 and 5.1.4. This may be the same fitting used in 7.4.3.

### 7.4.3 Short-Time Failure Pressure

Short-time hydraulic failure pressure testing shall be done in accordance with ASTM D 1599 (free end). Test sample includes a complete fiberglass connection. Failure pressure shall be greater than the published short-time hydraulic pressure in 8.1.h and greater than 85% of the minimum failure pressure of that component in the testing done in accordance with 5.1.2. Pipe and components furnished to this specification shall be tested in accordance with this paragraph at a minimum frequency of one test per lot. A pipe lot shall consist of 5,000 feet or fraction thereof for one size and wall thickness in continuous production. For other components, a lot shall consist of 100 units irrespective of size, type or pressure rating.

### 7.4.4 Visual Inspection

All pipe furnished to this specification shall meet the visual inspection limits in Table 3.

### 7.4.5 Retest

If any component fails to conform to the specified requirements 7.4.2 and 7.4.3, the Manufacturer may elect to make retests on two additional components from the same lot. If both of the retest specimens conform to the requirements, all remaining lengths in the lot shall be accepted. If one or both of the retest specimens fail to conform to the requirements, the tested lot shall be rejected. The Manufacturer may elect to test individually the remaining components from the rejected lot.

### 7.4.6 Wall Thickness

Total wall thickness shall be determined by caliper, eddy current thickness gage, or pi tape on the outside diameter and calculate thickness based on measured inside diameter on every joint away from the upset. Reinforced wall thickness shall be determined by ASTM D 3567 once every lot. Total and reinforced wall tolerances shall be as specified in Table 1.

### 7.4.7 Thread Gaging

Threads shall be gaged in accordance with API Recommended Practice 5B1. The minimum frequency of gaging shall be once per lot. For molded threads the first article from a new mold shall also be checked.

## 7.5 INSPECTION AND REJECTION

When stated on the purchase order, the provisions of Appendix E, Purchaser Inspection, shall apply.

## 7.6 QUALITY CONTROL RECORDS REQUIREMENTS

### 7.6.1 PURPOSE

The quality control records required by this specification are necessary to substantiate that all materials and products made to meet this specification do conform to the specified requirements.

### 7.6.2 Records Control

- a. Quality control records required by this specification shall be legible, identifiable, retrievable and protected from damage, deterioration, or loss.
- b. Quality control records required by this specification shall be retained by the Manufacturer for a minimum of five years following the date of manufacture.
- c. All quality control records required by this specification shall be signed and dated.

### 7.6.3 Records to be Maintained by Manufacturer

Test results in accordance with 7.4.

## 8 Published Values

### 8.1 PUBLISHED PROPERTIES

Certain properties do not have specified requirements but are nevertheless important in pipe system design. The Manufacturer shall perform the required tests and publish values for these additional pipe properties:

- a. Maximum Rated Temperature, °F.
- b. The LTHS and LCL as described in Paragraph 5.1.1.
- c. A value for the Thermal Coefficient of Expansion in the axial direction over the ranges from 32°F to 73.4°F, and from 73.4°F to the maximum rated temperature, shall be determined in accordance with the Manufacturer's written test procedure.
- d. Hoop tensile modulus at 73.4°F and at the maximum rated temperature in accordance with Appendix D.
- e. Poisson's ratio for a hoop tensile load and the resulting axial contraction at 73.4°F and at the maximum rated temperature in accordance with Appendix D.

f. Poisson's ratio for an axial tensile load and the resulting hoop contraction at 73.4°F and at the maximum rated temperature in accordance with Appendix F.

g. Axial Tensile Modulus of Elasticity at 73.4°F and at the maximum rated temperature in accordance with ASTM D 2105.

h. Short-term Hydraulic Failure Pressure of Pipe across the connection at 73.4°F and at the maximum rated temperature in accordance with ASTM D 1599 (free end).

### 8.2 PUBLISHED DIMENSIONS

Manufacturers shall publish the following information for each qualified products:

- a. Nominal ID.
- b. Nominal OD.
- c. Nominal Coupled Weight.
- d. Maximum Coupling or Integral Joint Outside Diameter.
- e. Nominal Wall Thickness.
- f. Minimum Reinforced Wall Thickness.

Table 3—Visual Standards

Defect	Description	Maximum Size
<b>Pipe Body and Component</b>		
Burn	Thermal decomposition evidenced by distortion or discoloration of the surface.	20% area—lightly blemished. 5% area—moderate burn of outer resin layer structural roving.
Chip	Small piece broken from edge or surface.	Permitted if laminate has not been fractured.
Crazing	Fine cracks at or under the surface as seen by the unaided eye.	None permitted.
Cut Roving	Broken or cut outer rovings due to scraping or scuffing or manufacturing process.	Maximum 3 per pipe with one square inch. Maximum size such that the wall thickness is not reduced below minimum.
Dry Spot	Area where reinforcement was not thoroughly wet with resin.	None permitted.
Fracture	Rupture of laminate without complete penetration. Visible as lighter colored area of interlaminar separation.	None permitted.
Pits (pinholes)	Small craters in the surface.	Maximum $1/16$ " deep, no limit on number.
Resin Drip	Resin protrusion.	Maximum $1/8$ " high, no limit on number.
Restriction	Any restriction: paste, epoxy or wax, lump, foreign matter in I.D. of pipe.	None permitted.
Scratch	Shallow mark caused by improper handling.	No limit on number if reinforcement is not exposed. If reinforcement is exposed, use cut roving.
Inclusions	Foreign matter wound into laminate.	None permitted.
<b>Threads</b>		
Air Bubbles	Small bubbles at crest of threads.	Maximum size $1/8$ ", one permitted per thread. Maximum size $1/16$ ", 10 permitted per thread.
Chips	Areas where over 10% of thread height is removed.	Maximum $3/8$ " long, one permitted per thread outside the $L_c$ area. None permitted in $L_c$ area.
Cracks	In direction of thread axis.	None permitted.
Flat Thread	Area where top of thread is broken or ground off.	Maximum $3/8$ " long, one permitted per thread outside the $L_c$ area, not to exceed 10% of the thread height. None permitted in the $L_c$ area.
Squareness	Angle perpendicular to thread, axis.	Maximum $1/16$ " variation in end.
Finish	Finish cut end.	No sharp edges. No exposed loose fiber. No protrusions. No impact areas.

## 9 Equipment Marking

### 9.1 METHODS

Components manufactured in conformance with this specification shall be marked by the Manufacturer as specified in 9.2. (Additional markings as desired by the Manufacturer or as requested by the Purchaser are not prohibited.) Markings shall be applied by paint or ink stencil, decal, or both. Markings shall not overlap and shall be applied in such manner as not to injure the pipe or couplings. Markings shall be legible for a period of three years in storage from the day of manufacture. Markings shall be applied on the pipe from one to three feet from the box connection.

### 9.2 COMPONENTS SHALL BE MARKED WITH THE FOLLOWING:

- a. Manufacturer's name or mark.
- b. "15HR"\* (and A.C. notation, if applicable).
- c. Nominal size.
- d. Unique identification number.
- e. Specification 15HR Standard Pressure Rating.
- f. Date of manufacture.

\*Users of the specification should note that there is no longer a requirement for marking a product with the API monogram. The American Petroleum Institute continues to license use of the monogram on products covered by this specification but it is administered by the staff of the Institute separately from the specification. The policy describing licensing and use of the monogram is contained in Appendix I herein. No other use of the monogram is permitted. Non-licensees may mark products in conformance with Section 9 and Licensees may mark products in conformance with Appendix I.

## 10 Handling, Packaging, Storing, and Shipping Requirements

### 10.1 COUPLING MAKEUP AND THREAD COMPOUNDS

All couplings shall be threaded onto the pipe by the manufacturer's documented make-up procedure; they shall be threaded on handling-tight, or shipped separately, if specified on the purchase order. A thread lubricant/sealant shall be applied to cover the full surfaces of the engaged threads of the coupling and pipe before making up the joint. The specified type of lubricant/sealant and makeup procedure shall be that recommended by the Manufacturer.

### 10.2 THREAD PROTECTORS

The Manufacturer shall apply external and internal closed end thread protectors to protect the ends and all exposed threads of the pipe, coupling and fitting from damage under normal handling and transportation. Thread protectors shall exclude foreign matter such as dirt from the ends and threads for storage.

Protector material shall be plastic and contain no compounds capable of damaging the threads or promoting adherence of the protectors to the threads and shall be suitable for service temperatures of -50° to +150° F.

### 10.3 FLANGE FACE PROTECTORS

Manufacturers shall apply flange face protectors to all flange faces in accordance with standard industry practice.

### 10.4 PACKAGING, SHIPPING AND HANDLING REQUIREMENTS

Manufacturers shall comply with Sections 1 and 2 of API Recommended Practice 15TL4.



## APPENDIX A—PRODUCT CHARACTERISTICS

It is the intention of this specification that ALL test samples be as representative of actual production line components as possible. The following characteristics must be the same for samples and production line components (within the manufacturer's documented production tolerances where applicable). Changes in the following characteristics of the piping system's components shall require testing in accordance with Section 5.4.

### A.1 Reinforcement

Manufacturer  
Production designation to include reference to:  
Mean Filament Diameter  
Finish (Sizing) Type and Amount  
Type (Single or Multiple End)  
Chemical Composition of Fiber  
Yield

### A.2 Resin Matrix

Manufacturer  
Product Designation

### A.3 Curing Agent

Manufacturer  
Product Designation

### A.4 Liner (if used)

Resin Manufacturer  
Resin Product Designation  
Reinforcement (if used) Subject to Above Characterization Thickness  
Cure Temperature and Time Schedule if Different From Component  
Curing Agent (Subject to Above Characterization)

### A.5 Adhesives

Manufacturer  
Product Designation

### A.6 Thread Molding Compounds

Manufacturer  
Product Designation

### A.7 Thread Sealing Compounds

Manufacturer  
Product Designation  
Generic Type  
Solids Weight Percent, Size Distribution, Material and Shape  
Physical Properties as Described in API Bulletin 5A2

### A.8 Joint Sealing Element

Manufacturer  
Product Designation  
Shore "A" Durometer Hardness  
Seal Dimensions

### A.9 Manufacturing\*

Cure Temperature and Time Schedule  
Winding Angle  
Stacking Sequence  
Percent Reinforcement in Each Direction  
Glass Transition Temperature as Determined in Appendix C  
Thread Dimensions as Specified in Section 5.3

### A.10 Report

Documentation of each applicable product characteristic shall be included for each component size and rating.

---

\*Recognize these parameters may be different for each size and rating.

**APPENDIX B—METRIC CONVERSIONS**

US Customary units are in all cases preferential and shall be the standard in this specification.

Length	1 inch (in.)	25.4 millimetres (mm) exactly
Pressure	1 pound per square inch (psi) Note: 1 Bar = 100 kilopascals (kPa)	0.06894757 Bar
Strength or Stress	1 pound per square inch (psi)	0.006894757 Megapascals (MPa)
Impact Energy	1 foot-pound (ft-lb)	1.3558181 Joules (J)
Torque	1 foot-pound (ft-lb)	1.3558181 newton-metres (N m)
Temperature	The following formula was used to convert degrees Fahrenheit (°F) to degrees Celsius (°C): $^{\circ}\text{C} = 5/9 (F - 32)$	
Mass	1 pound (lb)	0.4535924 kilograms (kg)

## APPENDIX C—TEST METHOD FOR DETERMINATION OF DEGREE OF CURE BY DIFFERENTIAL SCANNING CALORIMETRY (DSC)

### C.1 Scope

This test determines the degree of cure of a fiberglass pipe test specimen relative to statistically significant values obtained from typical production product.

### C.2 Definition

Glass transition temperature,  $T_g$ , is defined as the midpoint of the inflection temperature of the DSC curve (heat flow vs. temperature).

### C.3 Apparatus

Differential scanning calorimeter (DSC). The DSC equipment shall be calibrated in accordance to the DSC Manufacturer at a frequency specified by the DSC Manufacturer or at six-month intervals, whichever is shorter.

### C.4 Test Specimens

#### C.4.1 SIZE

The size of the specimen is limited by the size of the DSC sample pan. All specimens can be a chip or filed into a fine powder to provide easy weighing and uniform contact with the pan.

#### C.4.2 LOCATION

For any given tubular product, a sample shall be taken 0-10 mils from the outer surface for internally cured products, or 0-10 mils from the inner surface for externally cured

products. If the sample has a liner, then a specimen shall be taken from the liner as well as the inner or outer edges of the reinforced wall.

### C.5 Procedure

**C.5.1** Maximum heating rate is 40° C/minute.

**C.5.2** Run the scan from room temperature to at least 30° C above the expected glass transition temperature and no more than 250° C.

**C.5.3** Obtain the  $T_g$ .

### C.6 Report

The report shall include the following items.

**C.6.1** Complete identification of the specimens including material. Manufacturer's name, and lot number.

**C.6.2** Pipe dimensions, including nominal size, minimum reinforced wall thickness, and average outside diameter. Unreinforced thicknesses (i.e., liner) shall also be reported.

**C.6.3** Number of specimens tested and where the specimens were taken from the pipe.

**C.6.4** Heat-up rate for DSC temperature scans.

**C.6.5** Record glass transition temperature,  $T_g$ .

**C.6.6** Date of test.

**C.6.7** Test laboratory and supervisor of tests.

## APPENDIX D—DETERMINATION OF THE HOOP TENSILE MODULUS AND POISSON'S RATIO

### D.1 Scope

This appendix describes a method to determine the hoop tensile modulus and Poisson's ratio for a hoop tensile load and the resulting axial contraction.

### D.2 Definitions

**D.2.1** Hoop tensile modulus is defined as the hoop tensile stress divided by the hoop strain under the condition of uni-axial hoop tensile stress.

**D.2.2** Poisson's ratio is the ratio of axial strain to hoop strain as measured by strain gages with the tube pressurized to its rated pressure in accordance with this procedure.

### D.3 Apparatus

**D.3.1** A pressure source with a calibrated pressure measuring device.

**D.3.2** Strain gage monitoring equipment and gages.

**D.3.3** A test fixture as shown in Figure 1.

### D.4 Test Specimens

#### D.4.1 SIZE

The sample length,  $L$ , shall be at least ten times the nominal pipe outside diameter.

#### D.4.2 NUMBER OF SPECIMENS

Three specimens shall be tested for each pipe being evaluated.

**D.4.3** The samples selected shall be standard production pipe.

### D.5 Test Procedure

**D.5.1** Apply two strain gages to each specimen as shown in Figure 1. One strain gage shall be oriented to measure strain in the axial direction. The other strain gage shall be oriented to measure strain in the hoop direction. Standard strain gaging practices shall be followed.

**D.5.2** Insert the test fixtures into the test specimen as shown in Figure 1.

**D.5.3** Zero the strain gages.

**D.5.4** Pressurize the specimen to its rated internal pressure.

**D.5.5** Record the hoop and axial strain.

### D.6

Poisson's ratio is the axial strain divided by the hoop strain.

**D.6.1** Determine the hoop stress by the following formula:

$$h = P \frac{R_o^2 + R_i^2}{R_o^2 - R_i^2}$$

Where:

$h$  = hoop stress, psi

$P$  = internal pressure, psi

$R_i$  = the inside radius of the structural wall, inches

$R_o$  = the outside radius of the structural wall, inches

The inside diameter and structural wall thickness are determined by ASTM D 3567.

Hoop tensile modulus is the hoop tensile stress divided by the hoop strain.

### D.7 Report

The report shall include the following items.

**D.7.1** Complete identification of the test samples including material and Manufacturer's name.

**D.7.2** Pipe dimensions, including nominal size, reinforced wall thickness, inside diameter and length.

**D.7.3** The applied pressure.

**D.7.4** The measured hoop and axial strain, and the calculated hoop stress, for each sample.

**D.7.5** The mean hoop tensile modulus and Poisson's ratio.

**D.7.6** The test temperature.

**D.7.7** Start date and completion of tests.

**D.7.8** Test laboratory and supervisor of tests.

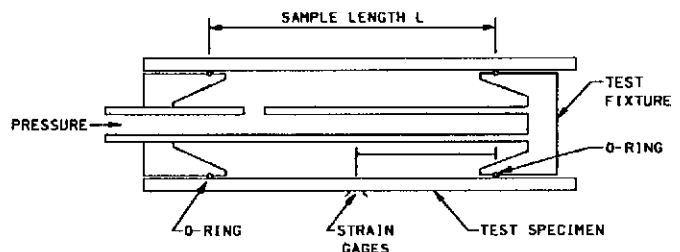


Figure 1—Typical Test Setup to Determine Hoop Tensile Modulus and Poisson Ratio

## **APPENDIX E—PURCHASER INSPECTION**

### **E.1 Inspection Notice**

Where the inspector representing the purchaser desires to inspect this pipe or witness these tests, reasonable notice shall be given of the time at which the run is to be made.

### **E.2 Plant Access**

The inspector representing the purchaser shall have unrestricted access at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which will concern the manufacture of the pipe ordered. The manufacturer shall afford the inspector all reasonable facilities to satisfy him that the pipe is being manufactured in accordance with this specification. All inspections should be made at the place of manufacture prior to shipment, unless otherwise specified on the purchase order, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

### **E.3 Compliance**

The manufacturer is responsible for complying with all of the provisions of this specification. The purchaser may make any investigation necessary to satisfy himself of compliance by the manufacturer and may reject any material that does not comply with this specification.

### **E.4 Rejection**

Unless otherwise provided, material which shows defects on inspection or subsequent to acceptance at the manufacturer's works, or which proves defective when properly applied in service, may be rejected, and the manufacturer so notified. If tests that require the destruction of material are made, any product which is proven to have not met the requirements of the specification shall be rejected. Disposition of rejected product shall be a matter of agreement between the manufacturer and the purchaser.

## APPENDIX F—DETERMINATION OF THE AXIAL TENSILE POISSON'S RATIO

### F.1 Scope

This appendix describes a method to determine the Poisson's ratio for an axial tensile load and the resulting hoop contraction.

### F.2 Definitions

**F.2.1** Poisson's ratio is the ratio of hoop strain to axial strain as measured by strain gages with the tube loaded to the axial load that would be produced at the rated pressure of the sample.

### F.3 Apparatus

**F.3.1** A testing machine and grips that meets the requirements set forth in Section 5.1, 5.1.1, 5.1.2, 5.1.3, 5.1.4, 5.1.5, and 5.1.6 of ASTM D 2105-85.

**F.3.2** Strain gage monitoring equipment and gages.

### F.4 Test Specimens

#### F.4.1 SIZE

The sample length shall be minimum of 18" between grips.

#### F.4.2 NUMBER OF SPECIMENS

Three specimens shall be tested for each pipe being evaluated.

**F.4.3** The sample selected shall be standard production pipe.

### F.5 Test Procedure

**F.5.1** Apply two strain gages to each specimen as shown in Figure D.1 of Appendix D. One strain gage shall be oriented to measure strain in the axial direction. The other strain gage shall be oriented to measure strain in the hoop direction. Standard strain gaging practices shall be followed.

**F.5.2** Insert the test sample into the testing machine per section 9.2 of ASTM D 2105-85.

**F.5.3** Zero the strain gages.

**F.5.4** Set the speed of testing per Section 9.3.1 or 9.3.2 of ASTM D 2105-85.

**F.5.5** Load the sample up to the axial load that would be produced at the rated pressure of the sample.

Note: If the correct equipment is available, the strains and loads can be recorded continuously, or per Section 9.4 of ASTM D 2105-85, and the sample taken to failure. This would allow the axial tensile modulus of elasticity to be determined at the same time as the Poisson's ratio. Follow ASTM D 2105-85, but use the axial tensile strain gage as the extension indicator.

### F.6

Axial Poisson's ratio is the hoop strain divided by the axial strain.

### F.7 Report

The report shall include the following items.

**F.7.1** Complete identification of the test samples including material and Manufacturer's name.

**F.7.2** Pipe dimensions, including nominal size, reinforced wall thickness, inside diameter and length.

**F.7.3** The applied load.

**F.7.4** The measured hoop and axial strain at the applied load for each sample.

**F.7.5** The mean axial tensile Poisson's ratio.

**F.7.6** The test temperature.

**F.7.7** Start date and completion of tests.

**F.7.8** Test laboratory and supervisor of tests.

## APPENDIX G—SERVICE (DESIGN) FACTORS

Consideration is being given to adopting a more comprehensive method of determining the pipe and prime connection pressure performance. The overall service (design) factor,  $S_f$ , in Equation 1, will be the product of the individual service factors thus permitting adjustment of the Specification 15HR Standard Pressure Rating for specific applications having other than the defined Standard Conditions.

$$S_f = SFC \times SFE \times SFL \times SFT \times SFA$$

Where:

- $S_f$  = overall service (design) factor (used in Equation 1)
- $SFC$  = Service Factor for cyclic pressure variations, which will be based on results of a test program currently being defined.
- $SFE$  = Service Factor for Environment, which will be based on a test program being evaluated.
- $SFL$  = Service Factor for design life, which will be defined as follows:

$$SFL = \frac{\text{LCL @ Design Life \& 150° F}}{\text{LCL @ 20 years \& 150° F}}$$

LCL at a higher temperature may be substituted for LCL @ 150° F.

$SFT$  = Service Factor for Temperature, which will be defined as follows:

$$SFT = \frac{\text{LCL @ Design Temperature \& 20 years}}{\text{LCL @ 150° F \& 20 years}}$$

LCL at a higher temperature may be substituted

for LCL @ 150° F. LCL at design temperature can be determined by interpolation when LCLs are available for temperatures higher and lower than the design temperature. Otherwise an LCL at a temperature higher than the design temperature shall be used.

At no time should a pipe be used for extended service at a temperature higher than that for which an LCL has been generated.

$SFA$  = Service Factor for additional axial loads (less than or equal to 1.0), which will be defined as follows:

$$SFA = \frac{\sigma AP - \sigma AA}{\sigma AP}$$

Where:

$\sigma AP$  = Axial stress due to the Specification 15HR pressure rating

$$= \frac{P_R R_i}{(R_o - R_i)}$$

$\sigma AA$  = Axial stress due to additional axial loads, for example bending a pipe to a certain radius of curvature, where  $\sigma AA$  would be calculated as shown.

$$\sigma AA = \frac{E_A R_o}{R_c}$$

Where:

$E_A$  = the axial modulus of elasticity, psi

$R_c$  = radius of curvature, inches

**APPENDIX H—DATA SHEET**

API Monogram required? Yes \_\_\_\_\_ No \_\_\_\_\_

Project(s) and location(s): \_\_\_\_\_

Maximum operating pressure: \_\_\_\_\_

Test Pressure: \_\_\_\_\_

Temperature ranges anticipated:

Minimum Ambient Temperature: \_\_\_\_\_

Maximum Fluid Temperature: \_\_\_\_\_

Anticipated composition of fluids: CO<sub>2</sub> \_\_\_\_\_ ppmH<sub>2</sub>S \_\_\_\_\_ ppm

Hydrocarbon Analysis (Gas, Oil)

Salt Water \_\_\_\_\_ %

Other \_\_\_\_\_

Anticipated future operations which would affect pressure, temperature, or fluid content:  
(e.g., hot-oiling) \_\_\_\_\_

Future Operating Parameters: \_\_\_\_\_

Will inhibitors be used? \_\_\_\_\_

If yes, what type? \_\_\_\_\_

Anticipated flow rates: \_\_\_\_\_ BPD oil/condensate

\_\_\_\_\_ MCF/D gas

\_\_\_\_\_ BPD salt water

Will erosion be a concern? \_\_\_\_\_ Cause: \_\_\_\_\_

Operator or third-party witness? Yes \_\_\_\_\_ No \_\_\_\_\_

Delivery requirements: \_\_\_\_\_

Special shipping, packing and storage instructions: \_\_\_\_\_

Technical contact in buyer's organization: \_\_\_\_\_

Phone: \_\_\_\_\_



## APPENDIX I—USE OF API MONOGRAM

### I.1 Reporting Requirements for API Licensees

Before a license to use the API monogram is granted, the manufacturer shall complete the report described in Par. 1.4.

### I.2 Marking Requirements for API Licensees

Components shall be marked with the following:

- a. Manufacturer's name or mark
- b. API monogram (and A.C. notation, if applicable)
- c. Nominal size
- d. Unique identification number
- e. Specification 15HR Standard Pressure Rating
- f. Date of manufacture
- g. API license number

## PUBLICATIONS LIST

The following publications are under the jurisdiction of the API Committee on Standardization of Fiberglass and Plastic Tubulars and are available from the American Petroleum Institute, 1220 L Street, Northwest, Washington, DC 20005: (202) 682-8375.

### SPECIFICATIONS

Spec 15HR *Specification for High Pressure Fiberglass Line Pipe.*

Covers high pressure fiberglass line pipe for use in the production of oil and gas.

Spec 15LE *Specification for Polyethylene Line Pipe.*

Provides standards for polyethylene (PE) line pipe suitable for use in conveying gas, oil and nonpotable water in underground service for the oil and gas producing industries.

Spec 15LR *Specification for Low Pressure Fiberglass Line Pipe.*

Covers low pressure fiberglass line pipe for use in conveying gas, oil, or nonpotable water in the oil and gas producing industries.

Spec 15LT *Specification for PVC Lined Steel Tubular Goods.*

Covers PVC liners in new or used steel pipe for use in conveying gas, oil or non-potable water in oil and gas producing industries.

### RECOMMENDED PRACTICES

RP 15TL4 *Recommended Practice for Care and Use of Fiberglass Tubulars.*

Provides information on transporting, handling and installing fiberglass casing, tubing, and line pipe in oil field usage.



ADDITIONAL COPIES AVAILABLE FROM  
PUBLICATIONS AND DISTRIBUTION  
(202) 682-8375

**American Petroleum Institute**  
1220 L Street, Northwest  
Washington, D.C. 20005



Order No. 811-15HR2